

Loughborough University Institutional Repository

3D printed dielectric Fresnel lens

This item was submitted to Loughborough University's Institutional Repository by the/an author.

Citation: ZHANG, S., 2016. 3D printed dielectric Fresnel lens. Presented at the 2016 10th European Conference on Antennas and Propagation, (EuCAP 2016), Davos, Switzerland, 10-15th April.

Additional Information:

- Personal use of this material is permitted. Permission from IEEE must be obtained for all other uses, in any current or future media, including reprinting/republishing this material for advertising or promotional purposes, creating new collective works, for resale or redistribution to servers or lists, or reuse of any copyrighted component of this work in other works.

Metadata Record: <https://dspace.lboro.ac.uk/2134/23067>

Version: Accepted for publication

Publisher: IEEE

Please cite the published version.

3D Printed Dielectric Fresnel Lens

Shiyu Zhang

School of Electronic, Electrical and Systems Engineering, Loughborough University, Loughborough, UK, LE11 3TU.
S.Zhang@lboro.ac.uk

Abstract— This paper presents the design and fabrication of a zone plate Fresnel lens. 3D Printing is used for rapid prototyping this low-cost and light-weight lens to operate at 10 GHz. This lens is comprised of four different 3D printed dielectric zones to form phase compensation in a Fresnel lens. The dielectric zones are fabricated with different infill percentage to create tailored dielectric constants. The dielectric lens offers 18 dBi directivity at 10 GHz when illuminated by a waveguide source.

Index Terms— Fresnel lens, zone plate, flat lens, additive manufacturing, 3D Printing

I. INTRODUCTION

Lens antennas have been widely studied due to the highly directional radiation, wide angle scanning and formed beam. The lenses are able to transform the spherical wave fronts into plane wave fronts to enhance the directivity of the antennas [1]–[5]. Fresnel lenses (FL) are relatively thin and flat, they usually have smaller volumes and weighs compared with conventional shaped lenses. They can be fabricated by using inexpensive dielectric materials, which makes them suitable for consumer applications [6]–[9].

The traditional fabrication approaches for dielectric lenses are dominated by using mechanical machining. The lens surface can be grooved to lead the wave have higher phase velocity by travelling through the grooved zones. Another method to accomplish the phase correction is to divide the lens into several concentric zones with different dielectric constants. This approach can be either realised by several tightly fitted concentric dielectric rings with various dielectric constants, or using uniform dielectric material that is perforated to create different dielectric zones [10], [11]. The FL that fabricated using the dielectric zones method generally has uniform thickness with flat surface, however the precisely machining is involved in which increases manufacturing complexity. Moreover, the machining technique removes or shapes parts of the raw materials which generates material waste.

The three-dimensional (3D) Printing technology constructs objects as successive layers. It is one-step process and able to generate complex internal structures. It significantly simplifies the manufacture process and reduces material waste. Furthermore, 3D Printing can create perforated structures that are difficult to be realised by machining due to the mechanical strength of material.

The dielectric materials can be custom-made by using 3D Printing [12]. By adjusting the infill percentage of the 3D material, it can create materials with bespoke structures with customised dielectric constant values. The 3D Printed dielectric materials which are cost efficient and can be rapidly prototyped. This gives engineers more freedom in antenna design.

This paper presents a novel dielectric FL that fabricated by using 3D Printing. In this work, an ABS based 3D Printing filament PREPERM[®] TP20280 was used. The dielectric constant of this 3D filament was characterised as 4.4 and loss tangent was 0.004. This material could be both injection moulded or extruded to form a designed shape. A fused deposition modelling (FDM) Makerbot[®] Replicator[™] 2X 3D-printer was used to fabricate the FL. The extrusion temperature was 230°C with the 110°C heated platform. The lens geometry was designed with radially varied infill percentages. Then the dielectrics were printed as non-solid which leads air voids into the lens and therefore the dielectric constants of the zones in the FL were tailor-fabricated. The entire FL was fabricated in one-step process.

II. PROTOTYPE DESIGN

The design of the FL was carried out at 10 GHz and the lens had a uniform thickness. The radii (R_i) for each dielectric zone can be determined using:

$$R_i = \sqrt{2iF \left(\frac{\lambda_0}{P}\right) + \left(i\frac{\lambda_0}{P}\right)^2} \quad i = 2, 3, \dots, P \quad (1)$$

Where P is the phase correcting index, λ_0 is the design wavelength and F is focal length. In this work the lens was designed for quarter wave phase correction. An $F/D = 0.3$ was chosen, to obtain a short focal length. The diagram of the FL is shown in Fig. 1. The focal length F was 30 mm.

The thickness of the lens t is related to the dielectric constants of two adjacent Fresnel zones and it can be obtained using:

$$t = \frac{\lambda_0}{P(\sqrt{\epsilon_s} - \sqrt{\epsilon_{s-1}})} \quad s = 2, 3, \dots, P \quad (2)$$

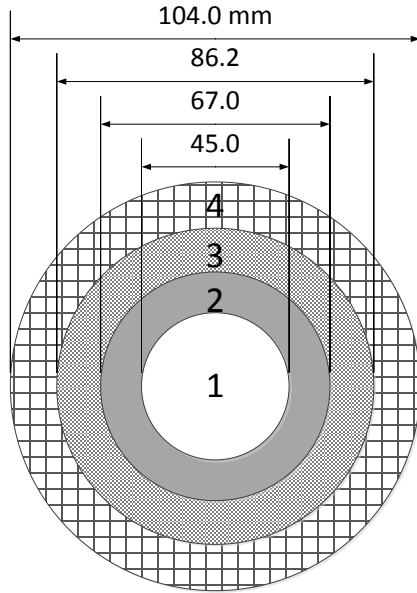


Fig. 1. Dielectric Fresnel lens design

In this design, the highest dielectric constant value was 4.4 which was realised by using 100% infill 3D material. In order to reduce the thickness and the weight, the centre ring with the minimum dielectric constant was equal to 1 which was air. Therefore the lens was made of three dielectric rings and one air ring per full-wave zone. By substituting $P = 4$, $t = 20.5$ mm, $\epsilon_{max} = 4.4$, $\epsilon_{min} = 1$ and $\lambda_o = 30$ mm into (2), the dielectric constant value for each ring could be obtained. The values with the corresponding infill percentages for the Fresnel zone radii are given in Table I.

TABLE I FRESNEL ZONE RADII AND CORRESPOND DIELECTRIC CONSTANTS

i	ϵ_r	R_i in mm	Infill percentage in %
1	1.0	22.5	0
2	4.4	33.5	100
3	3.0	43.1	58.8
4	1.9	52.0	25.6

III. RESULTS

A simulation was carried out using CST MICROWAVE STUDIO. The 3D modelling of this dielectric FL is shown in Fig. 2. The innermost ring was empty which had equivalent dielectric constant = 1. The empty centre significantly reduced the weight of the lens. A rectangular waveguide source with dimension of 22.86 mm \times 10.16 mm was located at the focal point on the lens axis.

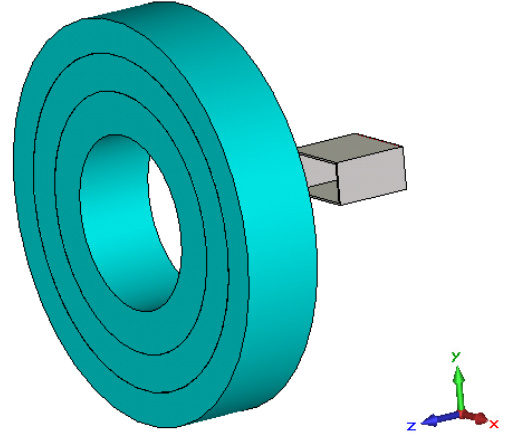


Fig. 2. The dielectric FL is illuminated by a rectangular waveguide source located on the axis

The simulated electric field in the XoZ plane of the dielectric FL with the waveguide source is shown in Fig. 3. It shows that FL reduced the width of the main radiation lobe of the source, which would enhance the directivity and led to an increased gain. The far field patterns of the dielectric FL at the frequency 10 GHz is shown in Fig. 4. This dielectric FL antenna had directivity 18.2 dBi. The directivity was significantly increased at boresight ($\theta = 0^\circ$). The -3 dB angular width was approximately 16° . Since this dielectric FL had a small focal length, the short distance between FL and waveguide reduced the side lobe level.

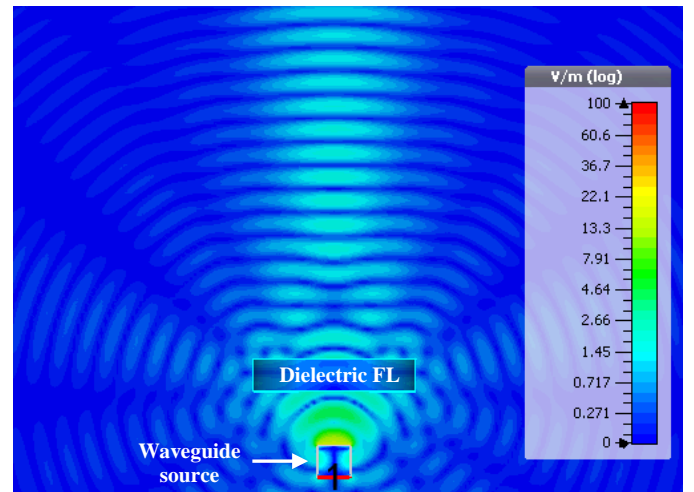


Fig. 3 Simulated electric field in XoZ plane of the dielectric FL with the waveguide source at 10 GHz

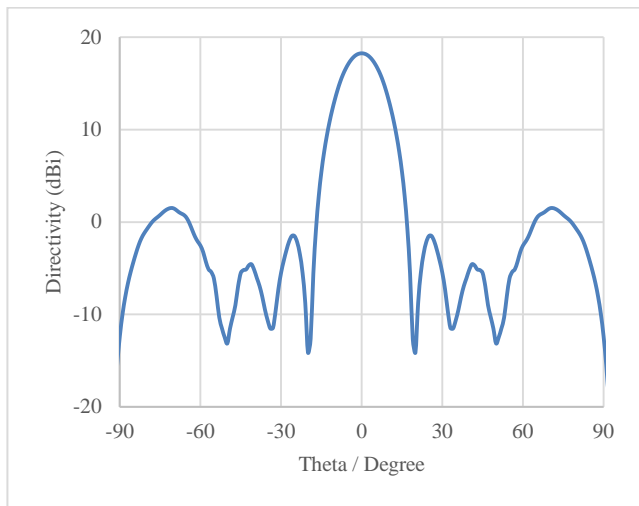


Fig. 4. Simulated Far field pattern of dielectric FL in XoZ plane at 10 GHz

IV. CONCLUSION

This paper has presented a low-profile and light-weight dielectric Fresnel lens. The 10 cm diameter prototype lens with 90° phase correction was comprised of three dielectric rings and one empty ring at the centre. The dielectric FL antenna offered directivity enhancement and suitable for various antenna applications.

The rapid prototyping 3D Printing technique was used for fabrication this dielectric lens to give bespoke dielectric constants for each ring. The dielectric rings were printed as non-solid internal structures with specific material infill percentage. The entire lens could be 3D printed in a single-step process without machining or assembling, which significantly simplified the manufacturing process.

ACKNOWLEDGMENT

The authors would like to thank the Premix for providing the 3D Printing filament.

REFERENCES

- [1] D. M. Pozar, "Flat lens antenna concept using aperture coupled microstrip patches," *Electronics Letters*, vol. 32, no. 23, p. 2109, 1996.
- [2] R. Yang, W. Tang, and Y. Hao, "A broadband zone plate lens from transformation optics," *Optics express*, vol. 19, no. 13, pp. 12348–12355, 2011.
- [3] Y. Zhang, R. Mittra, and W. Hong, "On the Synthesis of a Flat Lens using a Wideband Low-Reflection Gradient-Index Metamaterial," *Journal of Electromagnetic Waves and Applications*, vol. 25, no. 16, pp. 2178–2187, 2011.
- [4] H. F. Ma, B. G. Cai, T. X. Zhang, Y. Yang, W. X. Jiang, and T. J. Cui, "Three-dimensional gradient-index materials and their applications in microwave lens antennas," *IEEE Transactions on Antennas and Propagation*, vol. 61, no. 5, pp. 2561–2569, 2013.
- [5] A. D. Olver and B. Philips, "Integrated lens with dielectric horn antenna," *Electronics Letters*, vol. 29, no. 13, p. 1150, 1993.
- [6] D. N. Black and J. C. Wiltse, "Millimeter-Wave Characteristics of Phase-Correcting Fresnel Zone Plates," *Microwave Theory and*

Techniques, *IEEE Transactions on*, vol. 35, no. 12, pp. 1122–1129, 1987.

- [7] H. Hristov and M. Herben, "Millimeter-wave Fresnel-zone plate lens and antenna," *IEEE Transactions on Microwave Theory and Techniques*, vol. 43, no. 12, pp. 2779–2785, 1995.
- [8] H. D. Hristov and J. M. Rodriguez, "Design Equation for Multidielectric Fresnel Zone Plate Lens," *IEEE Microwave and Wireless Components Letters*, vol. 22, no. 11, pp. 574–576, Nov. 2012.
- [9] L. P. Kamburov, J. M. Rodriguez, J. R. Urumov, and H. D. Hristov, "Millimeter-Wave Conical Fresnel Zone Lens of Flat Dielectric Rings," *IEEE Transactions on Antennas and Propagation*, vol. 62, no. 4, pp. 2140–2148, 2014.
- [10] A. Petosa and A. Ittipiboon, "Design and performance of a perforated dielectric Fresnel lens," *IEE Proceedings - Microwaves, Antennas and Propagation*, vol. 150, no. 5, p. 309, 2003.
- [11] S. Petosa, A.; Ittipiboon, A.; Thirakoune, "Investigation on arrays of perforated dielectric fresnel lenses," *Microwaves, Antennas and Propagation, IEE Proceedings*, vol. 153, no. 3, pp. 270 – 276, 2006.
- [12] S. Zhang, C. C. Njoku, W. G. Whittow, and J. C. Vardaxoglou, "Novel 3D printed synthetic dielectric substrates," *Microwave and Optical Technology Letters*, vol. 57, no. 10, pp. 2344–2346, Oct. 2015.